

- Cite this as: He-dong LI, Shi-lang XU, 2016. Rate dependence of ultra high toughness cementitious composite under direct tension. *Journal of Zhejiang University-SCIENCE A (Applied Physics & Engineering)*, 17(6):417-426. <http://dx.doi.org/10.1631/jzus.A1600031>

## Rate dependence of ultra high toughness cementitious composite under direct tension

He-dong LI, Shi-lang XU

Key words: Ultra high toughness cementitious composite, Rate dependence, Direct tension, Strain hardening, Multiple cracking

# Background


- ❑ Most cementitious composites are strain-rate dependent.
- ❑ However ultra high toughness cementitious composite (UHTCC) possesses excellent static mechanical properties, what determines its effects in seismic application is its properties under high strain rates.
- ❑ There are limited researches conducted on the rate dependence of this type of multiple cracking strain hardening composites, and parts of their conclusions are different and even conflicting to each other.



**High flexural deformability**




**Saturated multiple cracking property**

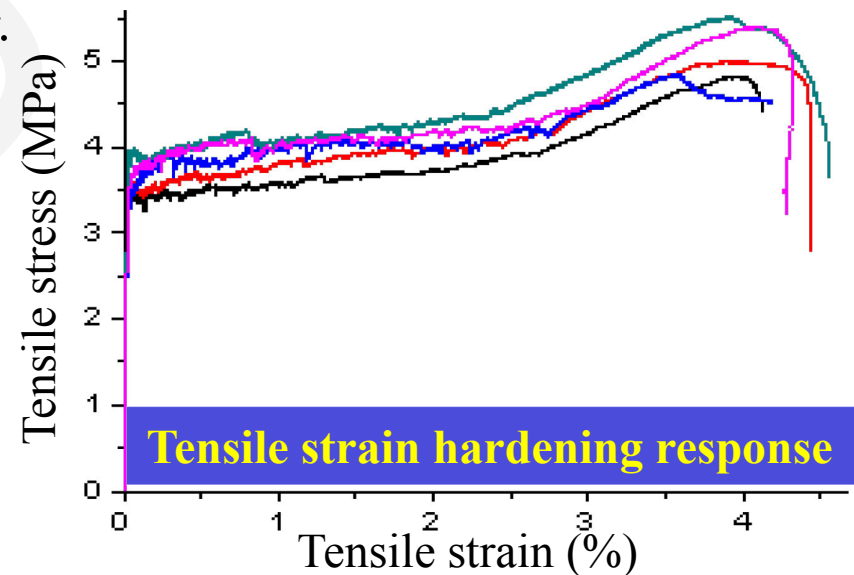

**Quasi-static tensile and flexural properties of UHTCC.**

# Method

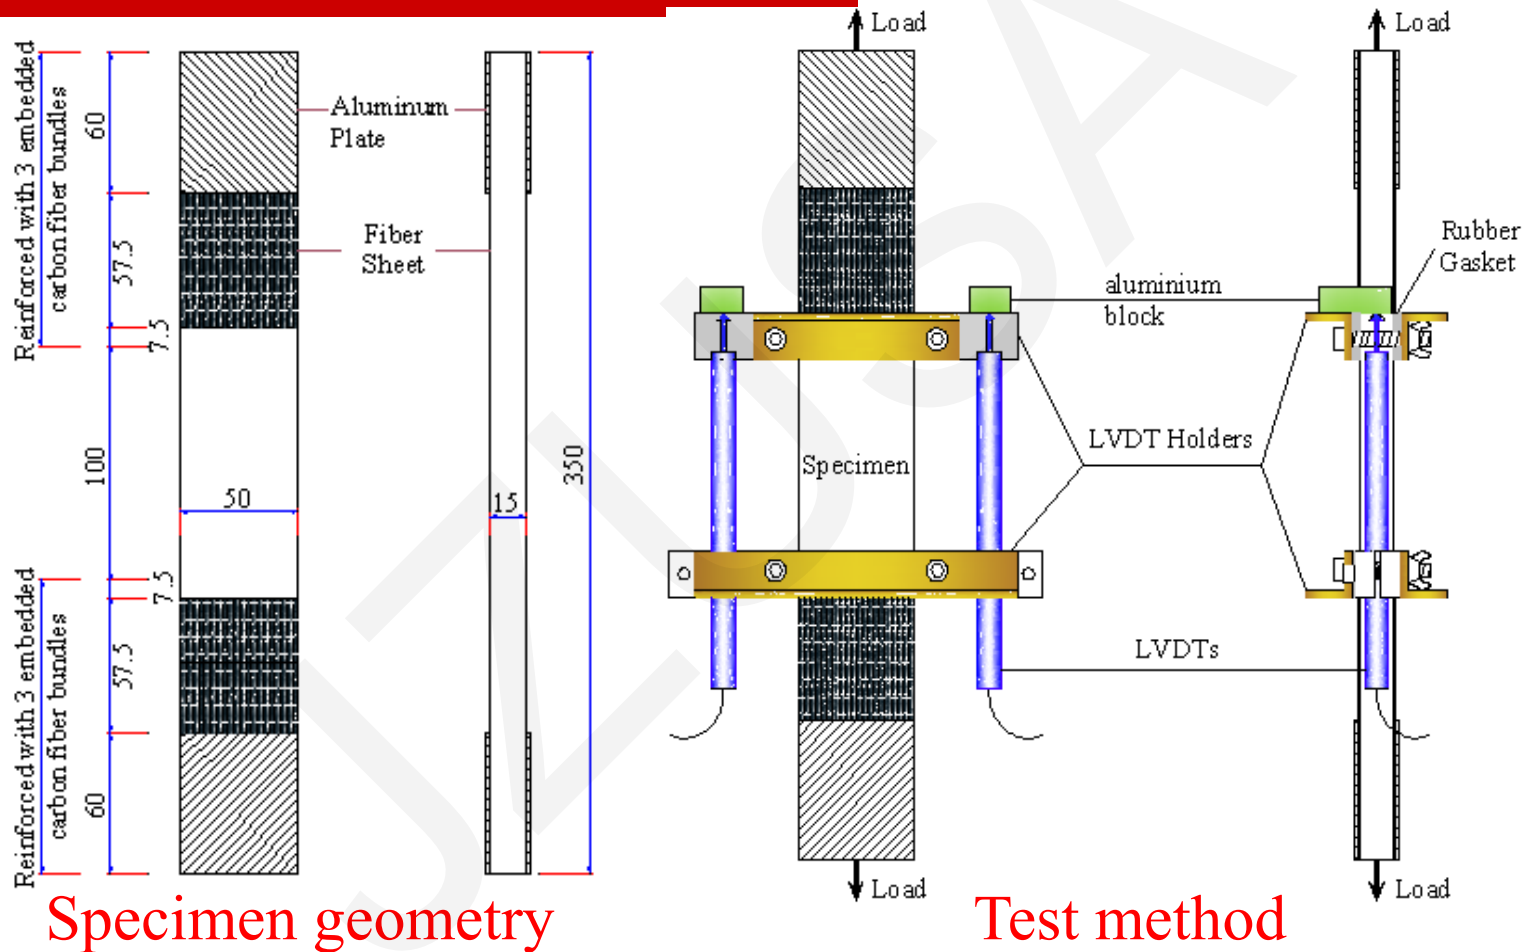


Specimen geometry

Test method


Loading rates:  $4 \times 10^{-6} \text{ s}^{-1}$ ,  $1 \times 10^{-5} \text{ s}^{-1}$ ,  $1 \times 10^{-4} \text{ s}^{-1}$ ,  $1 \times 10^{-3} \text{ s}^{-1}$ ,  $1 \times 10^{-2} \text{ s}^{-1}$ ,  $1 \times 10^{-1}$ , and  $4 \times 10^{-6} \text{ s}^{-1}$  is considered as the quasi static rate.

# Results and conclusions

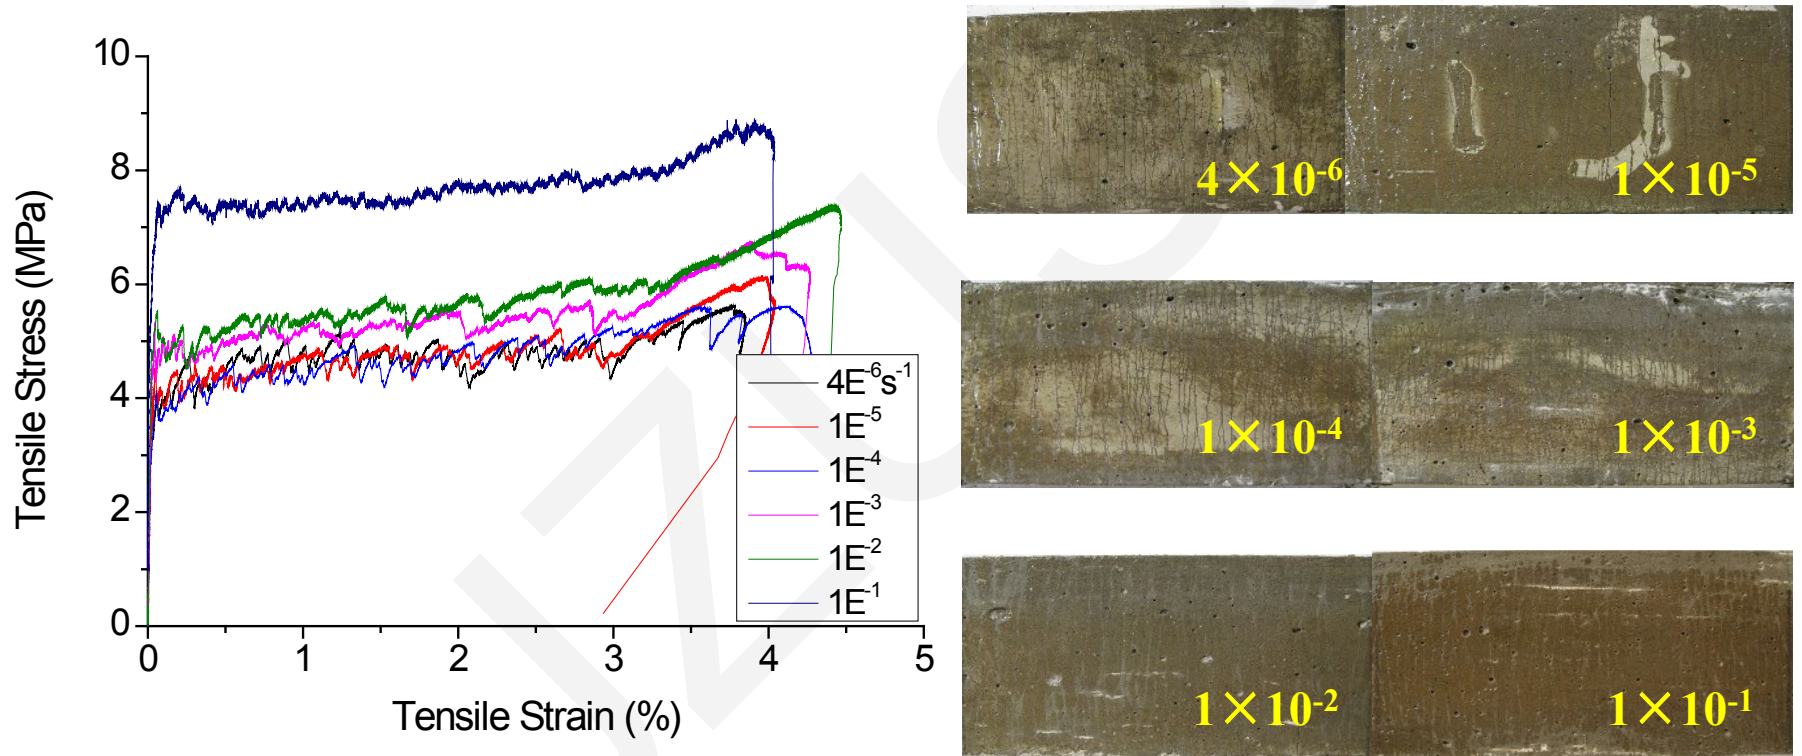


**Uniaxial tensile stress-strain curves and multiple cracking properties under different strain rates**


# Results

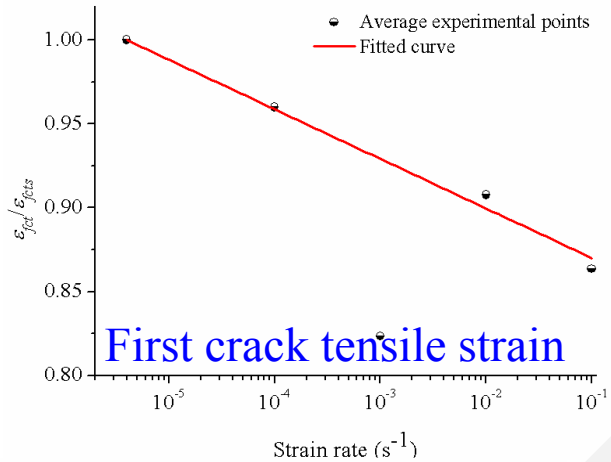


First crack tensile strain

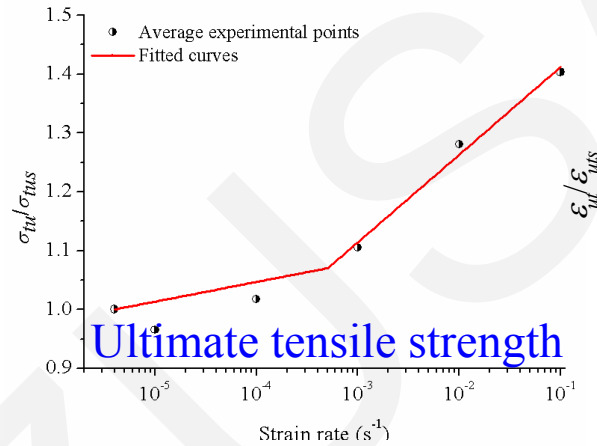


Ultimate tensile strength

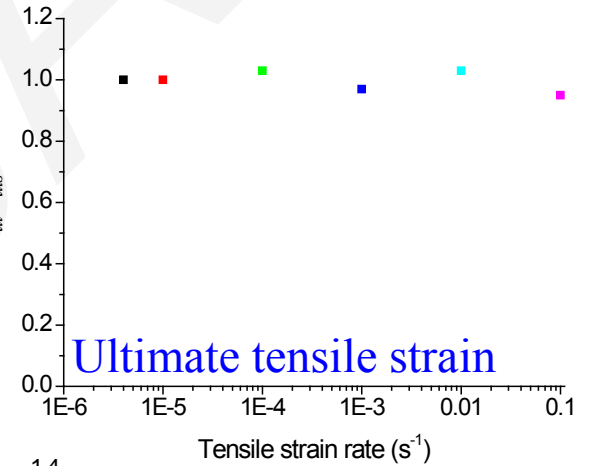


Ultimate tensile strain

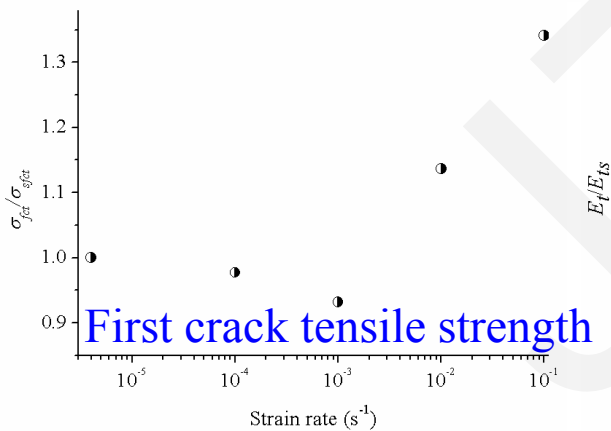

First crack tensile strength

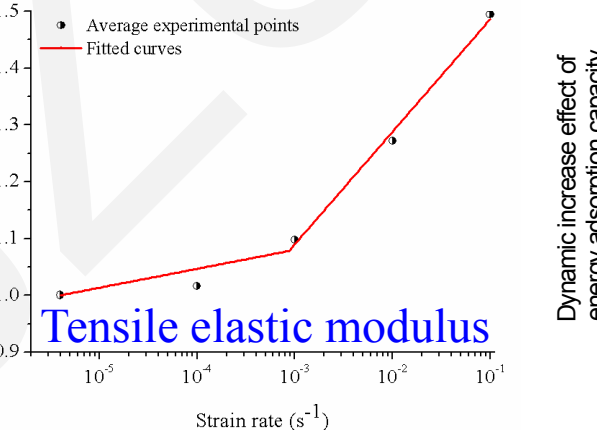

Tensile elastic modulus

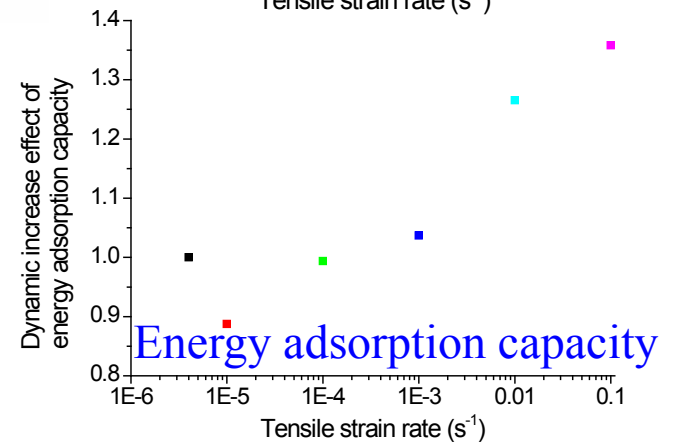

Energy adsorption capacity

Dynamic effects of tensile properties of UHTCC

# Conclusions

---

Based on uniaxial tensile tests on thin plate specimens of UHTCC with strain rates ranging from  $4 \times 10^{-6} \text{ s}^{-1}$  to  $1 \times 10^{-1} \text{ s}^{-1}$ , the following conclusions can be drawn:

- ❑ The first crack tensile strain, first crack tensile strength, elastic modulus, ultimate tensile strength and energy absorption capability of the UHTCC were all rate dependent. Except for the first crack tensile strain which showed a dynamic decrease effect, all others showed significant dynamic increase effects.
- ❑ The multiple cracking modes and ultimate tensile strain capacity of the UHTCC were both rate independent.
- ❑ The strain rate of  $1 \times 10^{-3} \text{ s}^{-1}$  seems to be the threshold for dynamic increase effects of first crack tensile strength, elastic modulus, ultimate tensile strength and energy absorption capacity of UHTCC. Their dynamic increase effects were not pronounced until the strain rate was higher than  $1 \times 10^{-3} \text{ s}^{-1}$ .
- ❑ UHTCC shows a great advantage over concrete in energy absorption capacity. Under seismic loads, the energy absorption capacity of UHTCC is about 1000 times that of C20 concrete.